

## Hegtdatos karima DIN 2633 (PN 16)



### Szabványok:


DIN 2500 "Karimák" (általános adatok)

DIN 2501 "Karimák" (csatlakozó méretek)

DIN 2519 "Acélkarimák" (műszaki szállítási feltételek)

DIN 2526 "Karimák" (tömítőfelület kialakítások)

Anyagok: RSt 37-2, C22.8, 15Mo3, 13CroMo44, 10CroMo910, 1.4541, 1.4571

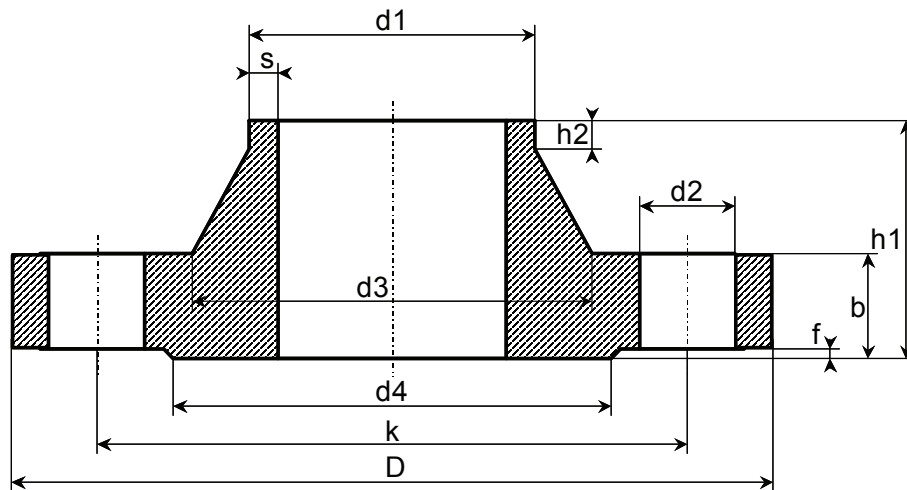

Névleges nyomás PN 16

DN	d1	D	b	k	h1	d3	s	h2	d4	f	d2	Csavarok	Súly/kg
125	133,0	250	22	210	55	150	4,0	12	188	3	18	8	6,300
125	139,7	250	22	210	55	156	4,0	12	188	3	18	8	6,300
150	159,0	285	22	240	55	175	4,5	12	212	3	22	8	7,750
150	168,3	285	22	240	55	184	4,5	12	212	3	22	8	7,750
175	193,7	315	24	270	60	210	5,4	12	242	3	22	8	9,850
200	219,1	340	24	295	62	235	5,9	16	268	3	22	12	11,000
250	267,0	405	26	355	70	285	6,3	16	320	3	26	12	15,600
250	273,0	405	26	355	70	292	6,3	16	320	3	26	12	15,600
300	323,9	460	28	410	78	344	7,1	16	378	4	26	12	22,000
350	355,6	520	30	470	82	390	8,0	16	438	4	26	16	31,200
350	368,0	520	30	470	82	390	8,0	16	438	4	26	16	28,800
400	406,4	580	32	525	85	445	8,0	16	490	4	30	16	39,300
400	419,0	580	32	525	85	445	8,0	16	490	4	30	16	36,300
500	508,0	715	34	650	90	548	8,0	16	610	4	33	20	61,000
600	610,0	840	36	770	95	652	8,8	18	725	5	36	20	75,400
700	711,0	910	36	840	100	755	8,8	18	795	5	36	24	77,000
800	813,0	1025	38	950	105	855	10,0	20	900	5	39	24	101,000
900	914,0	1125	40	1050	110	955	10,0	20	1000	5	39	28	122,000
1000	1016,0	1255	42	1170	120	1058	10,0	22	1115	5	42	28	162,000